

Verified
m

Journal of the Indian Institute of
Science.

V.10A Part-~~6~~, 1927.

Pp 65-69

JL ✓

A, d, m, N1415

N27.10A.6

196359 ✓

50

Price, As. 8.]


[Vol. 10A, Part VI, pp. 65 to 69.]

JOURNAL

OF THE

Indian Institute of Science.

CONTENTS.

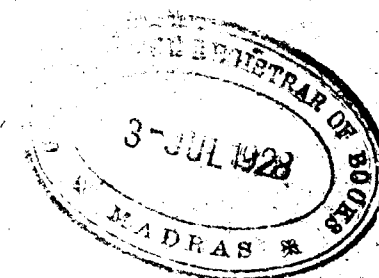

NOTE ON THE SORTING, CLASSIFICATION AND BRIQUETTING
OF CHROME AND MANGANESE ORES.

BY

K. R. Krishnaswami.

Received, 1941
110-59

M. O. FORSTER, F.R.S., CHAIRMAN OF EDITORIAL BOARD.

JOURNAL
OF THE
INDIAN INSTITUTE OF SCIENCE

Parts I.-XXI. VOLUME I.—(1914-18).
Parts I.-XV. VOLUME II.—(1918-19).
Parts I.-IX. VOLUME III.—(1920).
Parts I.-XVI. VOLUME IV.—(1921).
VOLUME V.—(1922).

Part I.—Studies in Acidolysis: I. The Equilibrium between Acetic Acid, Trichloroacetic Acid and their Ethyl Esters; II. The Equilibrium between Acetic Acid, Trichloroacetic Acid and their Methyl Esters. II.—An Attempted Synthesis of Norpinic Acid. III.—Experiments on the influence of *s*-Trinitrobenzene on Reactions in which Arylamines are involved. IV.—Induction Motors used as Synchronous Machines. V.—The Relation Between the Iodine Values and Refractive Indices of some Hardened Vegetable Oils, Part I. VI.—Performance of Three-phase Induction Motors on Unbalanced Voltages. VII.—The Production of Barium Salts from Barytes. VIII.—The Addition of Bromine to the α - and β -Chloro- and bromocinnamic Acids and their Esters. IX.—Oil Splitting by Castor-seed Lipase, Parts V-VII. X.—Some West Coast Vegetable Oils. XI.—Utilisation of Tamarind. XII.—West Australian 'Sandalwood Oil.' XIII.—The Extraction of Caffeine. XIV.—Mechanical Tests of Some Mysore Timbers.

VOLUME VI.—(1923).

Part I.—Mohua Oil. II.—Malabar Sardine Oil. III.—Studies in Esterification. IV.—The Action of Bases on $\alpha\alpha\beta$ - and $\alpha\beta\beta$ -Tribromo- β -phenylpropionic Acids and their Esters. V.—Hongay Oil. VI.—Cashew Kernel Oil. VII.—The Fruit of *Bassia longifolia*. VIII.—Studies in Intensive Bacterial Oxidation, I. The Oxidation of Alcohol to Acetic Acid. IX.—Contributions to the Study of the Prickly Pear Problem. X.—A Chemical Examination of Samples of Water and of Shells from the Inle Valley. XI.—The Refining of Crude Saltpetre. XII. Enolising Action of Hydrogen Chloride on Aldehydes and Ketones. XIII.—The Conversion of Eugenol into Isoeugenol.

VOLUME VII.—(1924).

Part I.—Studies in Alcoholysis V. The Alcoholysis of Esters of $\alpha\beta$ -unsaturated Acids and of the corresponding saturated Esters. II.—Chemical Factors in Denitrification. III.—The Retting of Coconut Husk for the Production of Coir. IV.—Reactions of Chromates at High Temperatures. Part I. The Synthesis and Decomposition of Calcium, Sodium and Magnesium Chromates in Air. V.—Oil from *Mimusops hexandra*; Rayan Oil. VI.—The Relation Between the Iodine Values and Refractive Indices of Hardened Oils. Part II. VII.—Contributions to the Scientific Study of the Lac Industry. Parts I-VIII. VIII.—I. The Systematic Nomenclature of Polycyclic Carbon Systems. II. Polycyclic and Cage Systems of Carbon Compounds. III. The Systematic Nomenclature of Heterocyclic Compounds including Polycyclic Structures. IX.—The Use of Mixed Catalysts in the Hydrogenation of Oils. X.—Condensation of Aromatic Amines with Chloroform or Carbon Tetrachloride in the Presence of Finely Divided Copper. XI.—I. Notes on H. II. An Alkaloid from *Anona*

Price, As. 8.]

[Vol. 10A, Part VI, pp. 65 to 69.

JOURNAL

OF THE

Indian Institute of Science.


CONTENTS.

NOTE ON THE SORTING, CLASSIFICATION AND BRIQUETTING
OF CHROME AND MANGANESE ORES.

BY

K. R. Krishnaswami.

DR. M. O. FORSTER, F.R.S., CHAIRMAN OF EDITORIAL BOARD.

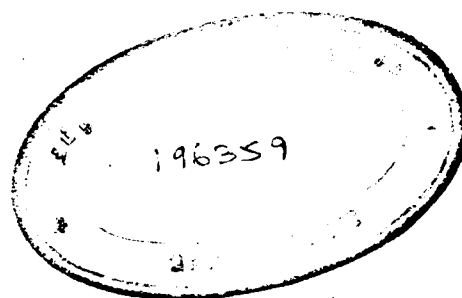

7L
A, d, m2, N1426
N27.10A.6.

NOTE ON THE SORTING, CLASSIFICATION AND BRIQUETTING OF CHROME AND MANGANESE ORES.

By K. R. Krishnaswami.

During mining operations it is inevitable that considerable quantities of low grade ore are obtained which cannot be disposed of profitably, while in the course of time there is a tendency for the quality of the ore to deteriorate owing to the removal of the higher grades. These facts have led to the extensive introduction of concentrating plant which has proved of the utmost value in many cases, particularly where sulphide ores are concerned. It is obvious, however, that when the ore-body is homogeneous or very nearly so, concentration is of little value.

In Mysore there are extensive deposits of chrome and manganese ores varying greatly in quality and it is a matter of some difficulty to distinguish the rich from the poor ore without recourse to analysis, consequently it was considered advisable to make a systematic examination of a number of samples in order to decide, if possible, the best means of recognizing the various qualities in the field. Some experiments were also made in concentrating some of the lower grade ores, and, in view of the fact that a great deal of the ore is in the form of powder which renders transportation somewhat difficult, attempts were made at briquetting this powder with various binding materials.

SORTING.

Samples of chromite from deposits at Arsikere, Sunkadahalli and Navale were examined. In most cases the ores could be sorted into well defined groups according to their appearance when broken. At Arsikere, five such types could be recognized but at Sunkadahalli only two. At Navale there is a reef of uniform appearance which cannot be classified, but boulders are also found in this locality and these can be separated into four types.

Lots weighing about 10 cwts. of each type were selected at the mine on different occasions by different people, crushed, sampled and analyzed. The results of the analyses of the different lots agreed within 1.5 per cent. for each type showing the reliability of the method. Table I shows the mean percentage of Cr_2O_3 in the various samples.

TABLE I.

Cr₂O₃ content of different types of chromite.

Type.	Navale.	Sunkadahalli.	Arsikere.	
	Cr ₂ O ₃ .	Cr ₂ O ₃ .	Cr ₂ O ₃ .	Density
Pink coarse grained	46.1	...	48.3	4.04
Pink fine grained	43.1	...	...	...
Dark steely	...	42.5	46.5	4.23
Pale steely	...	31.9	40.2	4.03
Yellowish brown	42.0	...	34.3	3.86
Do. do. speckled	38.4	...	...	...
Laminated	...	...	33.7	4.05

From these results it appears that although the appearance of the freshly broken surface affords a means of distinguishing high and low grade ores in different districts, it must not be assumed that samples of similar appearance from different localities will have the same chromium content. Nevertheless, the method is of considerable practical value when dealing with the output of a particular mine.

In the case of manganese no such correlation between fracture and composition has been found.

The densities of the Arsikere samples were measured, the values being shown in the last column of Table I, but these afforded no clue to the chromium content. This might be expected from the fact that the iron in chromite FeO. Cr₂O₃ may be replaced by magnesium and other substituents. Such a replacement would lower the density and increase the chromium content, while an admixture with foreign bodies or replacement of the Cr₂O₃ would lower both the density and the chromium content.

The density of a few samples of manganese ore was also determined. Specimens containing 52, 47, and 40 per cent. of Mn had specific gravities 4.29, 4.32, and 4.30 respectively so that in this case also there is no correlation.

CONCENTRATION.

100 lbs. lots of ore were crushed until the whole would pass through a 10 mesh sieve. By successive quartering and crushing a

sample of this was drawn and analyzed. About 60 lbs. of the powder were washed on a small laboratory Wilfley table and the concentrate and tailings collected in separate trays. The products were dried, weighed and analyzed. Table II shows the results obtained.

TABLE II

Results of concentrating chrome and manganese ores.

Mine.	Constituent.	Percentage in			Weight in lbs. of concentrate per 100 lbs. ore.	Percentage of total Cr ₂ O ₃ or Mn lost in tailings.
		Original ore.	Concentrate.	Tailings.		
Arsikere (a)	Cr ₂ O ₃	36.3	44.3	4.4	80	2.4
	FeO	22.3	18.4	...	...	...
	SiO ₂	8.7	6.3	...	...	...
Arsikere (a) 20 mesh	Cr ₂ O ₃	36.3	46.2	...	74	5.8
	SiO ₂	8.7	4.5	...	...	...
Arsikere (b)	Cr ₂ O ₃	22.0	42.9	...	47	8.4
	Cr ₂ O ₃	37.1	45.0	...	80	3.0
Sunkadahalli	FeO	22.7	18.3	...	...	...
	Cr ₂ O ₃	44.2	53.5	...	72	12.8
Bairapur	FeO	28.0	24.8	...	...	...
	Mn	33.5	42.8	19.0	62	20.8
Karekuchi	Fe	24.1	21.5	...	...	...
	SiO ₂	10.2	6.4	...	...	...
Mahadevpur	Mn	37.2	44.6	...	64	22.8

It is evident from these figures that considerable improvement in the quality of some chrome ores can be effected by this method with very little loss of chromium, but the results are not so satisfactory for the manganese ores.

BRIQUETTING.

If concentration of ores in the manner outlined were to be undertaken, a difficulty would arise with regard to the transportation of the product, since it has not so far been found practicable in this country to transport and ship powdered ores in bulk. The usual practice in the case of pyrolusite powder is to pack the mineral in bags, a somewhat costly method which does not entirely prevent loss of the contents.

SL
A.D. M2, 1415
N 27. 60. 6

The following experiments were made upon the feasibility of forming the powder into briquettes which could be transported in bulk.

1. *Tar*.—Wood tar was thickened by heating for some time at 100° and to the hot liquid the calculated quantity of concentrate was added gradually, mixing thoroughly after each addition. The mass was transferred to a brick-mould and well pressed in a firebrick press and then taken out of the mould. Some briquettes were allowed to dry in bright sunshine, some were heated for 3 days at about 100° and some others for the same time at about 400°. Although the proportion of tar was raised to 5 per cent. in no case was a satisfactory briquette obtained. Higher proportions of tar gave stronger briquettes but are prohibitive on account of the price.

2. (a) *Clay*, (b) *Lime* and (c) *Magnesia*.—Quantities of these up to 3 per cent. of the weight of the concentrate were added, mixed with enough water, and pressed into briquettes. The briquette obtained with bond (a) was heated at about 400° for 3 days and the others at 100° for the same time. The briquettes obtained were very weak.

3. *Magnesium Oxychloride*.—Various proportions of a mixture of magnesium oxide and chloride were thoroughly mixed with the concentrates, pressed and allowed to dry in the air. Even after 10 days the briquettes obtained were not strong enough for transit.

4. *Sodium Silicate*.—On mixing the concentrates with 1.5 per cent. of their weight of a warm 35 per cent. solution of sodium silicate and pressing the product a fairly satisfactory briquette was obtained even after air drying for about a week. If the briquette is kept at 200° for 2 days, it gets quite strong and remains intact even when dropped freely through about 3 feet on to a stone floor, but if heated to about 600° it becomes decidedly weaker. The cost of briquetting the concentrate by this method amounts to about Rs. 3 per ton, whereas bags for the same quantity cost at least Rs. 10.

SUMMARY.

1. The grade of a chrome ore can be ascertained with some exactness from its appearance when broken but this is not so in the case of manganese ores.

2. Specific gravity is not a reliable indication of the grade of chrome and manganese ores.


3. Several types of low grade chrome and manganese ores can be concentrated on the Wilfley table. In the case of chrome ores, the loss of chromium during concentration is small.

4. Sodium silicate is one of the best bonds for the briquetting of concentrates. Briquettes made with 1.5 per cent. of a 35 per cent. sodium silicate solution and heated to 200° are strong enough to withstand rough handling.

In conclusion it is my pleasant duty to thank Dr. Watson and Dr. Sudborough for their kind guidance and Mr. C. B. Oakley for generously providing the necessary facilities for the collection of the samples which were necessary for this work.

Department of General Chemistry,
Indian Institute of Science,
Bangalore.

[Accepted, 6-9-27.]

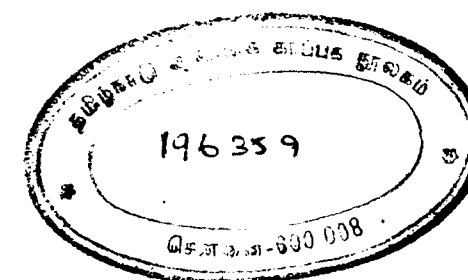

JL
A. d. m. 2. N. 11. 33
N 27-10A. 6

Squamosa Leaves. XII.—Iodine as a Catalyst in Reactions Involving Elimination of Hydrogen Halides. XIII.—Studies Relating to the Symbiosis of Seeds and Bacteria. XIV.—The Bio-Genesis of Mahua Oil. XV.—Contributions to the Scientific Study of the Lac Industry. Parts IX—X.

VOLUME VIII (A)—(1925).

Part I.—The Photochemical Oxidation of Aromatic Hydrocarbons. I. II.—Kachi-Grass Oil. III.—Argemone Oil. IV.—Essential Oil of *Cyperus Rotundus*. V.—Dehydration of Rectified Spirit by means of Anhydrous Calcium Chloride. VI.—The Hydrolysis of the Amides of $\alpha\beta$ -Unsaturated Acids and of their Saturated Analogues. VII.—I. Studies Relating to the Acetone-Producing Organisms. II. Mahua Flowers as Raw Material for the Acetone-Fermentation Process. VIII.—Studies in Esterification. IX.—Constituents of the Marking-Nut: '*Semecarpus Anacardium*' Linn. X.—Notes on Some Indian Essential Oils. XI.—Bromo-Derivatives of Para-Methoxycinnamic Acid. XII.—I. An Examination of Some Gum-Enzymes. II. Chemical Constitution of the Gum from '*Boswellia Serrata*'. XIII.—Industrial Wastes as Manure. I. Ajowan and Mohua Cakes as Fertilisers. II. Utilisation of Refuse. XIV.—Constitution of Manasse's Hydroxycamphor. XV.—The Reaction Between Sodium Sulphite and Sulphur. XVI.—The Occurrence of Sylvestrene.

VOLUME VIII (B)—1925.

Part I.—Lecher Wire Measurements. II.—The Aluminium Anode Film Dielectric.

VOLUME IX (A)—1926.

Part I.—Contributions to the Scientific Study of the Lac Industry. Part XI. Early Recognition of Sex among Lac Insects, by S. Mahdihassan. Price, Rs. 4.
Part II.—Vegetable Oils Containing Glycerides of Erucic Acid, by J. J. Sudborough, H. E. Watson and P. Ramaswami Ayyar. Price, Rs. 2-8.
Part III.—The Production of Ether by Solid Catalysts, by S. K. Kulkarni Jankar and H. E. Watson. Price Rs. 3.
Part IV.—The Constituents of Some Indian Essential Oils. Part XVIII. Derivatives of Abietic Acid, by Madyar Gopal Rao and John Lionel Simonsen. Price, As. 8.
Part V.—The Fat from '*Salvadora Oleoides*'. Khakan Fat, by C. K. Patel, S. Narayana Iyer, J. J. Sudborough and H. E. Watson. Price, As. 12.
Part VI.—The Constituents of Some Indian Essential Oils. Part XIX. The Essential Oil from the Rhizomes of '*Renealmia pulchra*' by Puthan Madhathil Bhaskara Panicker, B. Sanjiva Rao and John Lionel Simonsen. Part XX. The Essential Oil from the Rhizomes of '*Curcuma Aromatica*' Salisb., by B. Sanjiva Rao, Valarun Purushottam Shastri and John Lionel Simonsen. Part XXI. The Essential Oil from the Wood of '*Erythroxylon monogynum*' Roxb., by B. Sanjiva Rao, Valarun Purushottam Shastri and John Lionel Simonsen. Price, As. 12.
Part VII.—Reactions of Chromates at High Temperatures, Part II. The System $\text{CaO} - \text{Cr}_2\text{O}_3 - \text{O}_2$, by K. S. Narayana and H. E. Watson. Price, Rs. 1.
Part VIII.—I. The Catalytic Hydrogenation of Carone, by Subramania Narayana Iyer and John Lionel Simonsen. II. Conesine, by Darab Dhanu Kanga, Panchanada Ramaswami Ayyar and John Lionel Simonsen. Price, As. 8.

- and Naphthaisoquinolines. By Charles
Part IX.—Derivatives of Naphthaquinolines Krishna Hariharan, Kottiazath Narayana
Stanley Gibson, Kalvoi Venkata Menon. Price As. 12.
Menon and John Lionel Simonsen, Unstable Modification of *isoNitroso-*
Part X.—I. Isomeric Phenylserines. II. The *Gardenia Turgida*, by M. O. Forster
camphor. III. *d*-Mannitol. Rao. Price, As. 12.
and Keshaviah Aswath Narain

(B)—1926.

VOLUME IX

- ators, by K. P. Roy. Price, Re. 1.
Part I.—Double Synchronous Speed Alternating Transmitting Aerials, by J. K. Catterson-Smith.
Part II.—The Characteristics of Beam Transmitters Price, Re. 1, on-Smith. Price, Rs. 1-8.
Part III.—Aerial Testing, by J. K. Catterson-Smith. Price, Rs. 1-8.
Part IV.—Circulating Currents in Waveguides and G. K. Pradhan. Price, Rs. 1-8.
Part V.—Madras (Fort) Radio Field Intensity Measurements at Bangalore, by K. Sreenivasan. Price, Rs. 3.

(A)—1927.

VOLUME X

- Kottiazath Narayana Menon and John Lionel
Part I.—I. Some Reactions of Carone, by Kottiazath Narayana Menon and John Lionel
Simonsen. II. A Synthesis of Morindone, by Ramkanta Bhattacharya
and John Lionel Simonsen. III. Derivatives of Acenaphthopyridine. Part I, by Srikanth
Price, As. 12.
Part II.—Oils and Fats from the Seeds of Indian Forest Plants. Part VIII. The Oil
from the Seeds of *Neriifolia* (Juss.). By Ramkanta Bhattacharya. Part IX. The Oil from the Seeds of
charya and P. Ramaswami Ayyar. Part X. The Oil from the Seeds of
Cerbera Odollam (Gaertn.). Part XI. The Oil from the Seeds of
Holarrhena Antidysenterica. By Ramachandra Vishnu Ghanekar and
Anona *Squamosa* (Linn.). Price, As. 12.
P. Ramaswami Ayyar. Price, As. 12.
Part III.—Influence of the Sulphur Atom on Optical Rotatory Power. By
P. P. Shukla. Price, As. 8.
Part IV.—The Constitution of the Acid formed by the Action of Sulphuric Acid on
Camphorquinone. By Mahadev Balaji Bhagvat and John Lionel
Simonsen. Price, As. 8.
Part V.—*iso*Erucic Acid. By Tahilram Jethanand Mirchandani and John Lionel
Simonsen. Price, As. 8.
Part VI.—Note on the Sorting, Classification and Briquetting of Chrome and
Manganese Ores. By K. J. Krishnaswami. Price, As. 8.